



## Supported molybdenum carbides for higher alcohols synthesis from syngas

**Wu, Qiong Xiao; Christensen, Jakob Munkholt; Chiarello, Gian Luca; Temel, Burcin; Grunwaldt, Jan-Dierk; Jensen, Anker Degn**

*Published in:*  
American Chemical Society. Division of Fuel Chemistry. Preprints of Symposia

*Publication date:*  
2011

[Link back to DTU Orbit](#)

*Citation (APA):*  
Wu, Q., Christensen, J. M., Chiarello, G. L., Temel, B., Grunwaldt, J-D., & Jensen, A. D. (2011). Supported molybdenum carbides for higher alcohols synthesis from syngas. *American Chemical Society. Division of Fuel Chemistry. Preprints of Symposia*, 55(1).

---

### General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

# Supported molybdenum carbides for higher alcohols synthesis from syngas

Qiongxiao Wu<sup>1</sup>, Jakob M. Christensen<sup>1</sup>, Gian Luca Chiarello<sup>2</sup>, Burcin Temel<sup>3</sup>, Jan-Dierk Grunwaldt<sup>2</sup> and Anker D. Jensen<sup>1\*</sup>

<sup>1</sup> Department of Chemical and Biochemical Engineering, Technical University of Denmark,

Søltofts Plads, Building 229, 2800 Kgs. Lyngby (Denmark)

<sup>2</sup> Institute of Chemical Technology and Polymer Chemistry,

Karlsruhe Institute of Technology, Engesserstr. 20, 76131 Karlsruhe

<sup>3</sup> Haldor Topsøe A/S, Nymøllevej 55, 2800 Kgs. Lyngby (Denmark)

\* Corresponding author email address: AJ@kt.dtu.dk

## Introduction

The synthesis of higher alcohols ( $C_{2+}$  alcohols) has received a renewed attention lately for their application as alternative fuels and additives especially with syngas produced by biomass or coal gasification [1-4]. Previously, alkali modified bulk molybdenum carbide ( $\beta$ - $Mo_2C$ ) was shown to produce ethanol as the main alcohol product [5, 6]. However, the bulk  $\beta$ - $Mo_2C$  suffers from a low specific surface area, which results in low activity for CO hydrogenation [6]. Therefore, it would be interesting to determine a suitable support material for molybdenum carbide. This work provides an investigation of the high pressure CO hydrogenation to higher alcohols on molybdenum carbide based catalysts supported on various materials, *i.e.* active carbon, carbon nanotubes and titanium dioxide. The investigation includes also a comprehensive characterization of the catalysts by BET, X-ray diffraction (XRD), *in-situ* transmission electron microscopy (TEM) and X-ray absorption spectroscopy (XAS) investigations.

## Experimental

Molybdenum carbides supported on active carbon (AC), carbon nanotubes (CNTs), and titanium dioxide were prepared by temperature programmed reaction (TPR) of supported molybdenum oxide precursors in a flow of 20 vol%  $CH_4/H_2$ . These carbides were impregnated with an aqueous solution of  $K_2CO_3$  with calculated amounts. The performance of catalysts for higher alcohols synthesis (HAS) from syngas has been evaluated in a fixed-bed continuous-flow reactor with a GC-FID/TCD detection system. Prior to the reaction, the supported carbides were treated *in-situ* with 20%  $H_2$  in  $N_2$  flow (35 ml/min) at 350 °C for 2 h to remove a possible passivation layer formed after exposure in air. Typical operating conditions were: P=100 bar; T=250-300 °C; GHSV=5000  $h^{-1}$ ; Feed:  $H_2/CO=1$  (v/v). Particle sizes and phase compositions were investigated using XRD. The specific surface areas of both fresh and used catalysts were determined by  $N_2$  adsorption at 77 K. *In-situ* TEM was used to study the catalyst morphology in  $H_2$  gas flow from 25 to 600 °C. *In-situ* XAS, the Mo K-edge measurements were performed at the synchrotron of Hamburg HASYLAB-X beamline.


## Results and Discussion

Table 1 shows the catalytic performance of  $K_2CO_3/Mo_2C/TiO_2$  catalyst in CO hydrogenation at steady state. The CO conversion and selectivity to hydrocarbons were enhanced by increasing temperature, while the selectivity of methanol and higher alcohols decreased. The higher alcohols selectivity reached 34.3 mol% at 250 °C, however, the selectivity to both methanol and higher alcohols decreased dramatically when the temperature was increased. This may be caused by insufficient loading of the  $K_2CO_3$  promoter. Indeed, it has been observed for bulk  $Mo_2C$  that the selectivity to alcohols increases with increasing the  $K_2CO_3$  content up to 10 wt% and then stagnates [5]. Here 10 wt%  $K_2CO_3$  based on active materials ( $Mo_2C$ ) were

added for all catalysts and the dilution effect of support might be considered.

**Table 1.** Effect of temperature on the catalytic performance of  $K_2CO_3/Mo_2C/TiO_2$  in CO hydrogenation at steady state.

Catalyst	T [°C]	CO conv. [mol%]	Carbon based, CO <sub>2</sub> -free selectivity [mol%]		
			MeOH	C <sub>2+</sub> OH	HC
$K_2CO_3/Mo_2C/TiO_2$	250	4.6	18.1	34.3	46.2
$K_2CO_3/Mo_2C/TiO_2$	275	9.4	13.3	21.7	61.6
$K_2CO_3/Mo_2C/TiO_2$	300	85.1	0.3	0.43	99.3

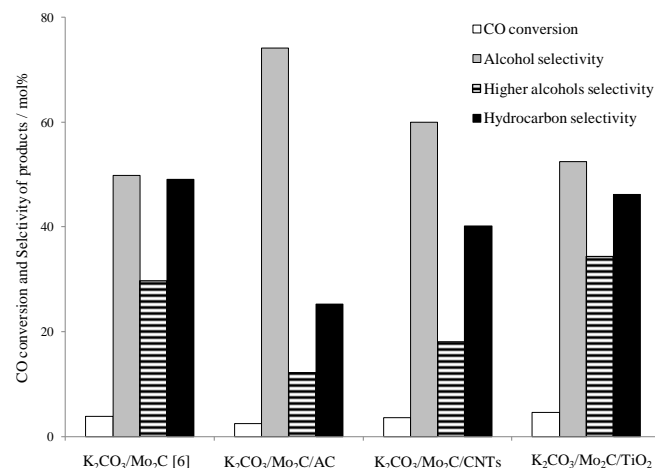

**Figure 1.** CO conversion and product selectivity (at 250 °C) at steady state over the investigated catalysts (5.3 wt%  $Mo_2C$  for all supported catalysts).

Figure 1 shows the CO conversion and the selectivity to different products at steady state. The active carbon supported catalyst exhibited the highest alcohols selectivity with methanol being the dominant alcohol. On the other hand,  $TiO_2$  supported catalyst showed the highest selectivity to higher alcohols.

## Conclusions

The catalytic activity of molybdenum carbides supported on different materials such as active carbon, carbon nanotubes, and titanium dioxide in higher alcohol synthesis from syngas is significantly affected by the support nature. In particular  $TiO_2$  seems to be a promising support due to its better selectivity to higher alcohols. The future work is focused on improving both the selectivity of the catalysts towards higher alcohols by modifying the  $K_2CO_3$  loading of the catalysts and the activity by increasing the loading of the  $Mo_2C$ .

## Acknowledgement

This work is financed by Technical University of Denmark, Haldor Topsøe A/S, and the Danish Ministry for Science, Technology and Development under the “Catalysis for Sustainable Energy” initiative.

## References

- (1) Subramani, V., and Gangwal, S.K. *Energy Fuels*, **2008**, 22(2), 814.
- (2) Spivey, J.J., and Egbebi, A., *Chem. Soc. Rev.*, **2007**, 36(9), 1514.
- (3) Christensen, J. M., Mortensen, P. M., Trane, R.; Jensen, P. A., Jensen, A.D. *Appl. Catal. A: General* **2009**, 366, 29.
- (4) Wender, I. *Fuel. Proc. Technol.*, **1996**, 48,189
- (5) Woo, H.C., Park, K.Y., Kim, Y.G., Nam, I.S., Chung, J.S., Lee, J.S., *Appl. Catal.* **1991**, 75, 267.
- (6) Christensen, J. M., Duchstein, L.D.L., Wagner, J.B. Temel, B., Jensen, P. A., Jensen, A.D. *submitted to Appl. Catal. A*, **2011**.